

Influence of Hole Doping on Antiferromagnetic Real-Space Approaches for the High-Tc Cuprates

Alexander Nazarenko¹, Stephan Haas², Jose Riera³, Adriana Moreo¹, and Elbio Dagotto¹

1. *Department of Physics, and National High Magnetic Field Lab, Florida State University, Tallahassee, FL 32306, USA*

2. *Theoretische Physik, Eidgenössische Technische Hochschule, 8093 Zürich, Switzerland*

3. *Instituto de Física Rosario, Avda. 27 de Febrero 210 bis, 2000 Rosario, Argentina*

Recently proposed scenarios for the cuprates make extensive use of a “flat” quasiparticle (q.p.) dispersion and short-range hole-hole interactions in real-space, both caused by antiferromagnetic (AF) correlations. The density of states (DOS) at half-filling has a robust peak which boosts the superconducting critical temperature T_c to large values as holes are introduced into the (rigid) q.p. band. Here, the stability of such scenarios is studied after a *finite* but small hole density is introduced. The overall conclusion is that the main features of real-space AF-based approaches remain qualitatively similar, namely a large T_c is found and superconductivity (SC) appears in the $d_{x^2-y^2}$ channel. As the hole density grows the chemical potential μ crosses a broad peak in the DOS. We also observe that extended s-wave SC competes with d-wave in the overdoped regime.

74.20.-z, 74.20.Mn, 74.25.Dw

The presence of “flat” regions in the normal-state q.p. dispersion is a remarkable feature of the phenomenology of hole-doped high temperature superconductors. [1] These flat bands are located around momenta $\mathbf{p} = (\pi, 0)$ and $(0, \pi)$, and at optimal doping they are $\sim 10\text{meV}$ below the Fermi energy, according to angle-resolved photoemission (ARPES) studies. [1] Antiferromagnetic correlations may play an important role in the generation of these features, as has been suggested by studies of holes in the 2D t-J and Hubbard models at and away from half-filling. [2–4] In addition, the flat regions induce a large peak in the DOS which can be used to boost T_c . This leads to a natural explanation for the existence of an “optimal doping” which in this framework occurs when the flat regions are reached by μ . We will refer to these ideas as the “Antiferromagnetic van Hove” (AFVH) scenario. [5] Superconductivity in the $d_{x^2-y^2}$ channel is natural in the AFVH scenario due to the strong AF correlations. [6,7] The interaction of holes is better visualized in *real space* i.e. with pairing occurring when dressed holes share a spin polaronic cloud, as in the spin-bag mechanism. [8] This real-space picture (see also Ref. [9]) holds even for a small AF correlation length, ξ_{AF} , and in this approach there is no need to tune parameters to work very close to an AF instability. Previous scenarios have also used van Hove (vH) singularities in the band structure to increase T_c , [10] but d-wave SC is not natural in this context unless AF correlations are included.

To obtain quantitative information from these intuitive ideas, holes moving with a dispersion calculated using one hole in an AF background, $\epsilon_{AF}(\mathbf{p})$, and interacting through a nearest-neighbors (NN) attractive potential, that mimics the sharing of spin polarons, have been previously analyzed. [5] Within a rigid band filling of $\epsilon_{AF}(\mathbf{p})$ and using a BCS formalism, $d_{x^2-y^2}$ superconductivity dominates with $T_c \sim 100K$ caused by the large DOS implicit in the hole dispersion. However, the accuracy of the rigid band approximation has not been studied before. In particular, the following questions arise: (i) does

the q.p. peak in the DOS found at $\langle n \rangle = 1$ survive a finite hole density?; (ii) how does the q.p. dispersion change with hole doping, and to what extent does this affect previous calculations in this framework?; (iii) are the “shadow” regions generated by AF correlations [8,11] important for real-space pairing approaches? In this paper all these issues are discussed. The overall conclusion is that as long as the hole density is such that the ξ_{AF} is at least of a couple of lattice spacings, the predictions of the original AFVH scenario [5] and other similar theories remain qualitatively the same.

To study the presence of a large DOS peak away from half-filling, $N(\omega) (= \sum_{\mathbf{p}} A(\mathbf{p}, \omega))$ has been calculated numerically in systems with strong AF correlations. While accurate extrapolations to the bulk limit are difficult, the simple qualitative picture emerging from these studies seems robust. In Fig.1a, $N(\omega)$ for the 2D t-J model obtained with exact diagonalization (ED) techniques is shown at several densities. [7] At half-filling, a large DOS peak caused by flat regions in the q.p. dispersion appears at the top of the valence band, as discussed before. [2] Weight exists at energies far from μ i.e. the large peak carries only part of the total weight. As shown in Ref. [2] the maximum in the DOS is *not* reached at the top of the valence band but at slightly smaller energies. As $\langle n \rangle$ decreases, the peak is now much broader but it remains well-defined. At $\langle n \rangle = 0.87$, μ is located close to the energy where $N(\omega)$ is maximized. If a source of hole attraction exists in this system, a SC gap would open at μ , and the resulting T_c could be large. However, even with $T_c \sim 100K$ the SC gap would not alter much the already robust peak in the DOS shown in Fig.1a. For $\langle n \rangle \sim 0.75$, μ moves to the left of the peak, where T_c should become smaller. Then, as $\langle n \rangle$ is reduced away from half-filling in the 2D t-J model Fig.1a suggests that μ travels across a broad DOS peak providing a natural definition for the “underdoped, optimal and overdoped” densities. [12] Note that since the peak width increases substantially with hole density, strictly speaking the rigid

band filling is invalid. However, such an approximation may have captured the qualitative physics of the problem, as discussed in this paper, since the DOS peak is not washed out by a finite hole density.

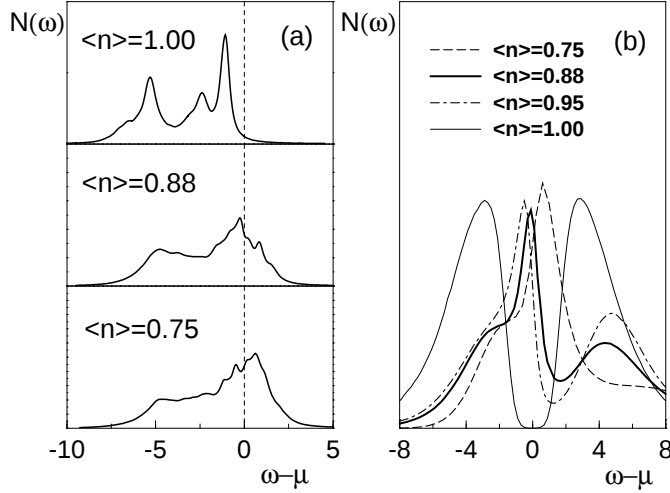


FIG. 1. (a) $N(\omega)$ for the 2D t-J model averaging results for clusters with 16 and 18 sites, at $J/t = 0.4$ and for the densities indicated. The δ -functions were given a width $\eta = 0.25t$. Similar results were found at other values of J/t ; (b) $N(\omega)$ for the one band Hubbard model obtained on a 4×4 cluster using QMC and ME. The temperature is $T = t/4$ and $U/t = 12$. Densities are indicated. Previous studies showed that QMC/ME results are only weakly affected by size effects.[3]

Quantum Monte Carlo (QMC) data for the 2D one-band Hubbard model in strong coupling indicate a qualitative behavior similar to that of the t-J model, i.e. μ also crosses a peak as $\langle n \rangle$ varies. This effect was observed in previous simulations, [13] and also in our own studies (Fig.1b). [14] However, note that QMC simulations must be supplemented by a Maximum Entropy (ME) analysis to obtain $N(\omega)$. ME predictions are more accurate close to $\omega \approx 0$ than at finite frequency, and thus we here do *not* interpret Fig.1b as suggesting the “generation” by doping of a Kondo-like peak at the top of the valence band which does not exist at $\langle n \rangle = 1$. We believe that the absence of a sharp peak at half-filling is caused by the systematic errors of the ME procedure and the finite temperature of the simulation. Actually, a robust peak at $\langle n \rangle = 1$ appears in other computational studies, [2,13] and in the t-J model (Fig.1a). Experimentally in the cuprates it has been already established [15] that the states observed in PES upon doping are already present in the insulator and are *not* Kondo resonances. In the present calculation, Fig.1a suggests that the broad peak observed at $\langle n \rangle < 1$ in the t-J model is smoothly connected to the sharper peak found at half-filling.

Similar conclusions can be reached in geometries other than the 2D square lattice. In particular, we studied the DOS of the t-J model on a *ladder*, finding results very

similar to those of Fig.1a, in agreement with previous calculations. [16] Note that on ladders the presence of pairing at finite hole density has been predicted. [17] Thus, a gap may open at μ once couplings and lattice sizes are reached where pairing effects are important. We have observed such effects in our studies, but we also found that at $\langle n \rangle = 1$ the DOS has a sharp peak, as in Fig.1a. Then, the ladder DOS peak is not exclusively caused by a BCS-induced redistribution of spectral weight upon doping.

In all cases discussed here, calculations of the spin-spin correlations show that ξ_{AF} is approximately a couple of lattice spacings when μ is located near the DOS peak, becoming negligible as the overdoped regime is reached. Thus, a nonzero ξ_{AF} and μ near a large DOS peak are *correlated* features. It is in this respect that scenarios where AF correlations produce a large DOS that enhances T_c differ from vH theories where divergences in the DOS are caused by band effects already present before interactions are switch on.

While the existence of a robust peak in the DOS is in good agreement with ARPES data, [1] it is in apparent disagreement with specific heat studies for YBCO which have been interpreted as corresponding to a flat DOS. [18] The lack of $\mathbf{p}$ -resolution in the specific heat measurements may solve this puzzle. Actually, angle-*integrated* PES results for Bi2212 do not show the sharp flat features found in ARPES for the same material. [15,19] Similar effects may affect the specific heat data.

Now let us discuss the $\mathbf{p}$ -dependence of the q.p. band obtained from $A(\mathbf{p}, \omega)$. Results are already available in the literature. [3,20] In Fig.2a-b, the q.p. dispersion is shown at $\langle n \rangle = 1$, and at $\langle n \rangle \sim 0.87$ for the t-J model. [20] Note that upon doping the small q.p. bandwidth and the flat regions remain well-defined, inducing a large DOS peak (Figs.1a). However, the region around $\mathbf{p} = (\pi, \pi)$ has changed substantially, i.e. the AF shadow region clearly observed at $\langle n \rangle = 1$ has reduced its intensity and considerable weight has been transferred to the inverse PES region (Fig.2b). Actually, the q.p. dispersion at $\langle n \rangle \sim 0.87$ can be fit by a tight-binding nearest-neighbors (NN) dispersion with a small effective hopping likely associated with J . This effect was also noticed in studies of the Hubbard model. [21,3,4].

The changes in the q.p. dispersion with hole doping can be interpreted in two ways: First, note that $A(\mathbf{p}, \omega)$ is influenced by matrix elements of *bare* fermionic operators connecting states with N and $N \pm 1$ particles. This is important when the q.p. weight is small i.e. when the state $c_{\mathbf{p}\sigma}|gs\rangle_N$ does not have a large overlap with the ground state of the $N - 1$ particles subspace $|gs\rangle_{N-1}$ ($|gs\rangle_N$ being the ground state with N particles). It has been suggested [22,23] that if the hole excitation is created by a new operator $\gamma_{\mathbf{p}\sigma}$ that incorporates the dressing of the hole by spin fluctuations, then $\gamma_{\mathbf{p}\sigma}|gs\rangle_N$ may now have a large overlap with $|gs\rangle_{N-1}$. In other words, if the dressed hole state resembles an extended spin polaron, then the physics deduced from PES studies, which rely on the sudden removal of a bare electron from the

system, may be misleading. To the extent that spin polarons remain well-defined at finite density, the use of $\gamma_{\mathbf{p}\sigma}$ will induce spectral weight rearrangements between the PES and IPES regions, and Fig.2b could resemble Fig.2a after such spectral weight redistribution takes place, as some results already indicate. [23] If this idea were correct, then the study of SC and transport, both regulated by *dressed* quasiparticles, could indeed be handled by filling a rigid band given by $\epsilon_{AF}(\mathbf{p})$.

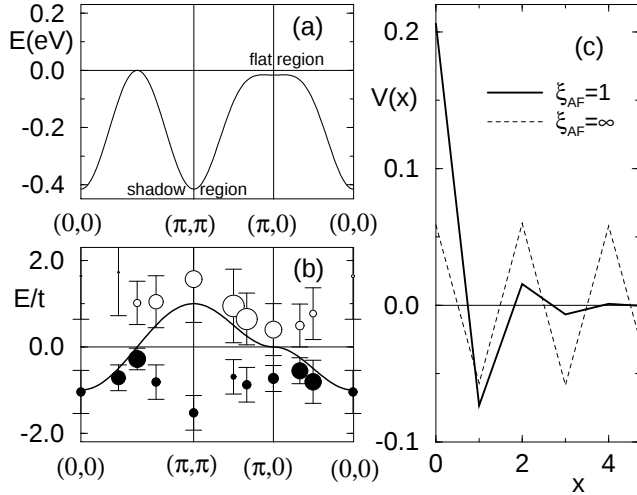


FIG. 2. (a) q.p. energy vs momentum obtained at half-filling.[2] The result shown, $\epsilon_{AF}(\mathbf{p})$, is a good fit of Monte Carlo data on a 12×12 cluster at $J/t = 0.4$; (b) q.p. dispersion vs momentum at $\langle n \rangle = 0.87$ and $J/t = 0.4$ using exact diagonalization of 16 and 18 sites clusters (from Ref.[19]). The open (full) circles are IPES (PES) results. Their size is proportional to the peak intensity. The solid line is the fit $\epsilon_{NN}(\mathbf{p})$; (d) $V(x)$ along the x -axis after Fourier transforming the smeared potential $V(\mathbf{p}) = \delta(\mathbf{p} - \mathbf{Q})$ (see text). ξ_{AF} is given in lattice units.

However, an alternative is that the difference between Figs.2a and 2b corresponds to an intrinsic change in the q.p. dispersion as ξ_{AF} decreases. This is the less favorable case for the AFVH approach, and thus we analyze this possibility in detail here. For this purpose, we have applied the standard BCS formalism to a model with a low density of q.p.'s having a dispersion $\epsilon_{NN}(\mathbf{p})/eV = -0.2(\cos p_x + \cos p_y)$, which roughly reproduces the dominant features of Fig.2b. As before, we include NN attraction between q.p.'s. While naively it may seem dubious to use the same interaction both at and away from half-filling, the hole-hole potential should not be much affected at distances shorter than ξ_{AF} . This can be illustrated by a real space analysis (Fig.2c) of a smeared δ -function potential of AF origin $V(\mathbf{q}) = \xi_{AF}/[1 + \xi_{AF}^2(\mathbf{q} - \mathbf{Q})^2]$, where the lattice spacing is set to 1, and $\mathbf{Q} = (\pi, \pi)$. Fig.2c shows that the NN potential ($x = 1$) does not change noticeably as ξ_{AF} is reduced, while $V(x > 1)$ is rapidly suppressed. Then, using the same NN form of the potential for many densities

is justified. Note also that the local character of the real-space potential does *not* imply small Cooper pairs. Their size can be regulated using both its range *and* intensity.

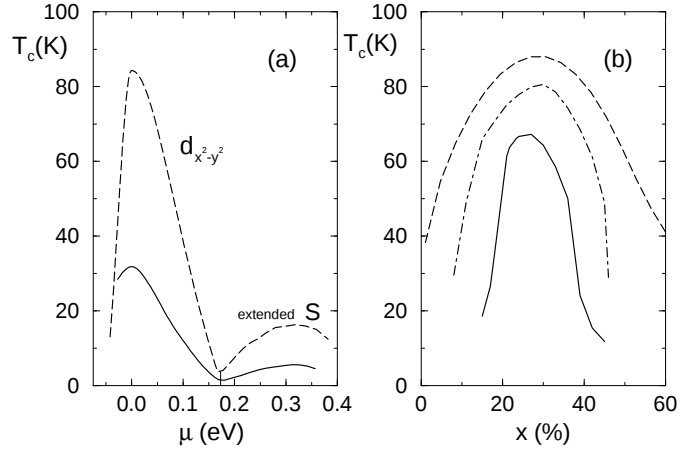


FIG. 3. (a) T_c vs μ obtained with the BCS gap equation, with $\mu = 0$ as the chemical potential corresponding to the saddle-point. The dashed line corresponds to $\epsilon_{AF}(\mathbf{p})$, and the solid line to $\epsilon_{NN}(\mathbf{p})$. Interpolations between these two extreme cases can be easily constructed using two band models with weights regulated by Z -factors. Note the presence of both $d_{x^2-y^2}$ -wave and extended s-wave SC; (b) T_c for d-wave SC vs the percentage x of filling of the q.p. band (not of the full hole spectrum). The dashed line is the same as in (a). The solid line corresponds to the BCS gap equation result making zero the weight $Z_{\mathbf{p}}$ of states in the q.p. dispersion that are at energies from the saddle point larger than 2.5% of the total bandwidth (i.e. basically including states only in a window of energy $\sim 125K$ around the flat regions). The dot-dashed line is the same but using a window of $\sim 250K$ around the flat regions.

Then, let us discuss the results obtained using the BCS formalism with an attractive NN potential $V = -0.6J$, [5] with $J = 0.125eV$, for both dispersions $\epsilon_{AF}(\mathbf{p})$ and $\epsilon_{NN}(\mathbf{p})$. Solving numerically the gap equation, T_c is shown in Fig.3a. As reported before, [5] SC at $T_c \sim 80 - 100K$ in the $d_{x^2-y^2}$ channel appears naturally if the AF-dispersion is used. If, instead, $\epsilon_{NN}(\mathbf{p})$ is used, the flat bands present in this narrow dispersion produce $T_c \sim 30K$ which is still large. Even more remarkable is the fact that the $d_{x^2-y^2}$ character of the SC state is maintained. This result can be understood noticing that a combination of $\epsilon_{NN}(\mathbf{p})$ with an attractive NN potential effectively locates us in the family of “t-U-V” models with U repulsive and V attractive, where it is known that for a “half-filled” electronic band the dominant SC state is $d_{x^2-y^2}$ -wave. [24] In other words, when μ is at the flat region in Fig.2b it approximately corresponds to a “half-filled” q.p. band, leading to a $d_{x^2-y^2}$ -wave SC state (Fig.3a). [25] Then, one of our main results is that even if the q.p. dispersion changes substantially with doping near the $\mathbf{Q}$ point, such an effect does *not* alter the main qualitative features found in previous studies.

[5]

The present analysis also shows that the AF “shadow” regions of $\epsilon_{AF}(\mathbf{p})$ are not crucial for the success of the real-space approach. Actually, using $\epsilon_{NN}(\mathbf{p})$, which does not contain weight in PES near (π, π) , T_c is still robust and the d-wave state remains stable. To make this point more clear, we analyzed T_c using $\epsilon_{AF}(\mathbf{p})$ but modulating the contribution of each momentum with a $\mathbf{p}$ -dependent weight $Z_{\mathbf{p}}$ in the one particle Green’s function. We considered the special case where $Z_{\mathbf{p}}$ is zero away from a window of total width W centered at the saddle point, which is located in the flat bands region. Inside the window W , $Z_{\mathbf{p}} = 1$. Such a calculation also addresses indirectly possible concerns associated with widths $\sim (\epsilon(\mathbf{p}) - \epsilon_F)^2$ that q.p. peaks would acquire away from half-filling in standard Fermi liquids. Results are shown in Fig.3b, for d-wave SC. Note that even in the case where W is as small as just 5% of the total bandwidth (itself already small of order $2J$), T_c remains robust and close to $70K$. Then, it is clear that the dominant contribution to T_c comes from the flat regions and the shape of the q.p. dispersion away from them is not relevant for the success of the real-space approach.

We end this paper with novel predictions obtained from $\epsilon_{AF}(\mathbf{p})$ and $\epsilon_{NN}(\mathbf{p})$, when μ reaches the bottom of these bands (which should *not* be confused with the bottom of the full hole spectrum since a large amount of weight lies at energies lower than those of the q.p. band). In this regime, the BCS analysis applied to any of the two dispersions shows that extended *s*-wave SC dominates over $d_{x^2-y^2}$ -wave SC in the “overdoped” regime (Fig.3a). This occurs when the q.p. band is nearly empty which, according to Fig.1a, corresponds to an overall density of $\langle n \rangle \sim 0.7$. This change in the symmetry of the SC state can be understood recalling again that $\epsilon_{NN}(\mathbf{p})$, supplemented by a NN attraction formally corresponds to an effective “t-U-V” model. It is well-known that in this model the SC state symmetry changes from d- to s-wave as the density is reduced away from half-filling to a nearly empty system. [24,26] Actually the bound state of two particles with a NN tight binding dispersion and NN attraction is *s* – *wave*. To the extent that the AF- or NN-dispersions survive up to $\sim 25\%$ hole doping, as suggested by numerical data, [13,20] scenarios based on the real-space interaction of q.p.’s predict a competition between extended s-wave and $d_{x^2-y^2}$ -wave SC in the *overdoped* regime. It is remarkable that calculations based on the analysis of the low electronic density $\langle n \rangle \ll 1$ limit of the t-J model lead to analogous conclusions. [27,26] Our approach is based on a very different formalism, but it arrives to similar results, and thus we believe that a crossover from d- to s-wave dominated SC in overdoped cuprates could occur. Recent ARPES data for overdoped Bi2212 have indeed been interpreted as corresponding to a mixing of s- and d-wave states. [28]

Summarizing, the predictions of real-space theories based on dispersions and interactions calculated at half-filling are qualitatively stable upon the introduction of

a finite hole density. These include a large T_c , within the BCS formalism, and SC in the $d_{x^2-y^2}$ channel. In the overdoped regime a possible crossover from d- to extended s-wave SC was discussed.

We thank A. Fujimori, D. Dessau, Z.X. Shen, and D. M. Edwards for useful correspondence. E. D. and A.M. are supported by grant NSF-DMR-9520776. We thank the NHMFL and MARTECH for additional support.

-
- [1] D.S. Dessau et al., Phys. Rev. Lett. **71**, 2781 (1993); K. Gofron et al., Phys. Rev. Lett. **73**, 3302 (1994).
 - [2] E. Dagotto, A. Nazarenko and M. Boninsegni, Phys. Rev. Lett. **73**, 728 (1994).
 - [3] N. Bulut, D. J. Scalapino and S. R. White, Phys. Rev. B **50**, 7215 (1994).
 - [4] R. Preuss, W. Hanke, and W. von der Linden, Phys. Rev. Lett. **75**, 1344 (1995); R. Putz, R. Preuss, A. Muramatsu and W. Hanke, Phys. Rev. **B**, April 1996.
 - [5] E. Dagotto, A. Nazarenko and A. Moreo, Phys. Rev. Lett. **74**, 310 (1995).
 - [6] D. J. Scalapino, Phys. Rep. **250**, 331 (1995).
 - [7] E. Dagotto, Rev. Mod. Phys. **66**, 763 (1994).
 - [8] A. Kampf and J.R. Schrieffer, Phys. Rev. **B 41**, 6399 (1990).
 - [9] Q. P. Li, B. E. C. Koltenbah, and R. J. Joynt, Phys. Rev. **B 48**, 437 (1993).
 - [10] C. C. Tsuei et al., Phys. Rev. Lett. **65**, 2724 (1990); R. S. Markiewicz, J. Phys. Condens. Matt. **2**, 6223 (1990); A. A. Abrikosov et al., Physica **C 214**, 73 (1993).
 - [11] P. Aebi et al., Phys. Rev. Lett. **72**, 2757 (1994); S. Haas et al., Phys. Rev. Lett. **74**, 4281 (1995).
 - [12] Recent specific heat calculations for the 2D t-J model are compatible with the presence of a maximum in $N(\omega)$ near half-filling (J. Jaklic and P. Prelovsek, preprint).
 - [13] N. Bulut, D. J. Scalapino and S. R. White, Phys. Rev. Lett. **72**, 705 (1994).
 - [14] Recently, Ulmke et al. (preprint) reported $N(\omega)$ using QMC on a 4^3 3D cluster, with results similar to Fig.1b.
 - [15] A. Fujimori et al., Phys. Rev. **B 39**, 2255 (1989); Phys. Rev. **B 40**, 7303 (1990).
 - [16] M. Troyer, H. Tsunetsugu, and T. M. Rice, preprint.
 - [17] E. Dagotto and T. M. Rice, Science **271**, 618 (1996).
 - [18] J. W. Loram et al., Phys. Rev. Lett. **71**, 1740 (1993).
 - [19] J. M. Imer et al., Phys. Rev. Lett. **62**, 336 (1989).
 - [20] A. Moreo et al., Phys. Rev. **B 51**, 12045 (1995).
 - [21] E. Dagotto, F. Ortolani and D. Scalapino, Phys. Rev. **B 46**, 3183 (1992).
 - [22] E. Dagotto and J. R. Schrieffer, Phys. Rev. **B 43**, 8705 (1991).
 - [23] R. Eder and Y. Ohta, Phys. Rev. **B 50**, 10043 (1994).
 - [24] R. Micnas et al., Rev. Mod. Phys. **62**, 113 (1990).
 - [25] For a different approach arriving to similar conclusions see J. Beenen and D. M. Edwards, J. of Low Temp. Phys. **99**, 403 (1995).
 - [26] E. Dagotto et al., Phys. Rev. **B49**, 3548 (1994).
 - [27] B. E. C. Koltenbah and R. Joynt, preprint, Jan. 1996. See

- also D. van der Marel, Phys. Rev. **B 51**, 1147 (1995).
- [28] J. Ma, C. Quitmann, R. J. Kelley, H. Berger, G. Margaritondo, and M. Onellion, Science **267**, 862 (1995).